Boral Construction Materials
Materials Technical Services

Unit 4, 3-5 Gibbon Road,
Baulkham Hills NSW 2153 Australia
PO Box 400,
Winston Hills NSW 2153

T +61 (02) 9624 9900
boral.com.au

TEST REPORT – CURING COMPOUND

CLIENT: EVENRANGE PTY LTD

ADDRESS: 12 Frankston Garden Drive, Carrum Downs, VIC 3201

FILE NO: 258/26
REQUEST NO: 122919

LAB. SAMPLE NO: 334301

TEST METHOD: AS 3799 – 1998 - Liquid Membrane-forming Curing Compounds for Concrete

DISTRIBUTOR: PARCHEM
SAMPLE IDENTIFICATION: CONCURE WB30 WHITE – Sample No. 60123
SAMPLE DESCRIPTION: Wax based curing compound
CLASSIFICATION: CLASS A, TYPE 2
SAMPLE SOURCE: VIC
DATE SAMPLED: UNKNOWN **DATE RECEIVED:** 17/02/2026

METHOD OF APPLICATION: by spraying at standard application rate of 5 m²/L.

TEST RESULTS:

Standard property, Test (Method)	Specification	Result	Date Tested
Water retention efficiency AS 3799.3.1.2 (Appendix B)	Min. 90%	97%	27/02-02/03/2026
Non - volatile content* AS 3799.3.1.8 (Method AS 1580.301.1)	N / A	32.55%	06/03/2026
Density* AS 3799.3.1.9 (Method AS/NZS 1580.202.1)	N / A	0.958 kg/L	24/02/2026
Viscosity* AS 3799.3.1.5 (Method AS/NZS 1580.214.5)	Min. 0.05 Pa.s (emulsions) Min. 0.02 Pa.s (solutions)	0.17 Pa.s	02/04/2026
Drying Time* AS 3799.3.1.4 (Appendix C)	Max. 4 Hrs	4 Hrs	06/03/2026
Infrared absorption spectrum* AS 3799.3.2 (Boral In-house Method)	N / A	Attached	17/04/2026
Stability of emulsion* TfNSW T862	Max. 4%	0.61%	10/03/2026
Residue 150µm* AS 3799.3.1.6 (Method AS/NZS 2341.26)	Max. 0.2%	0.2%	10/04/2026

Notes:


- Sample was provided by the client and tested as received.
- * Test method is not in the current scope of NATA Accreditation for the Boral MTS laboratory.

Approved signatory _____ Sam El-Hamawi

Date 21/04/2026 Serial no. CEM122919.SE.2

Accredited for compliance with ISO/IEC 17025 – Testing
This report shall not be reproduced in full without the approval of the Boral MTS Laboratory.
Test results in this Test Report relate only to the samples tested.

NATA Accredited Laboratory
Number: 547

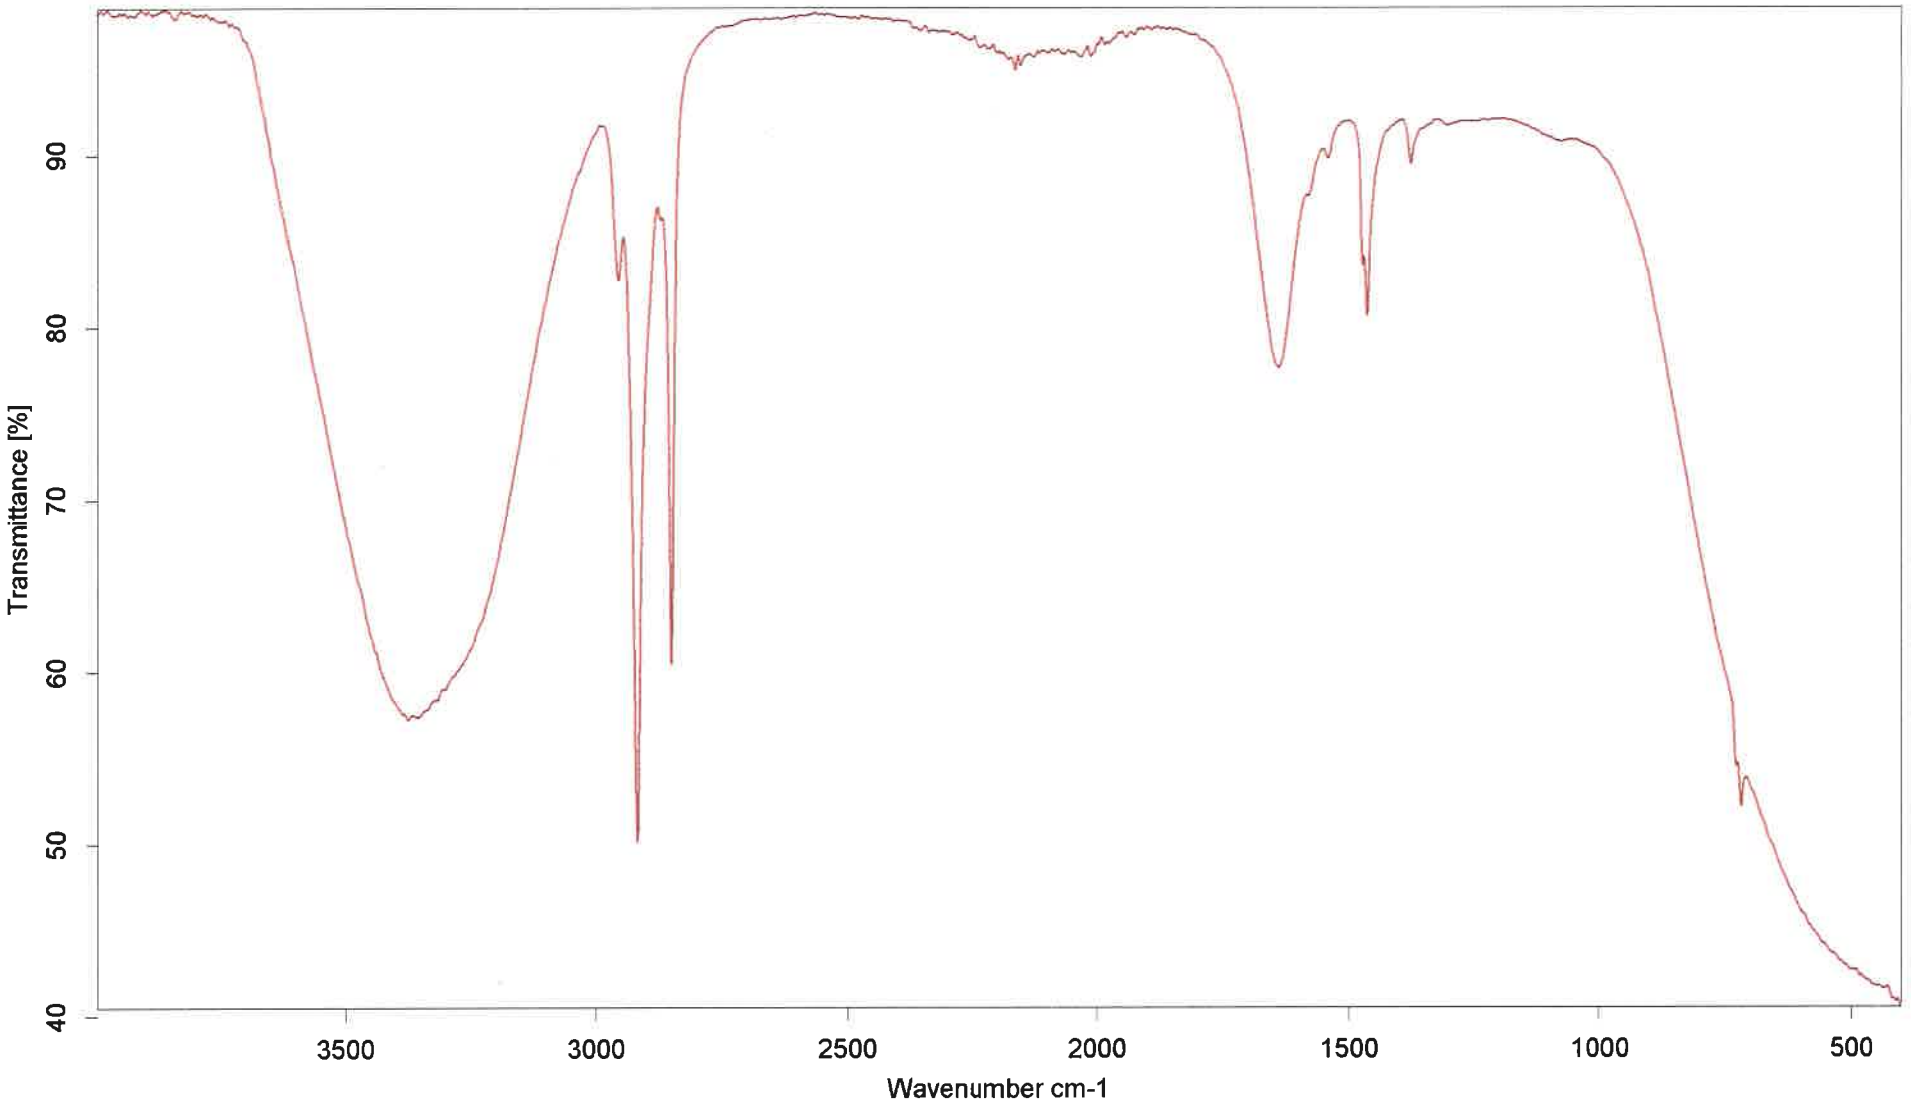

LSN 334301 Concure WB30 White wax Based Curing Compound Type 2, Class A Sample No: 60123 Rec. 17/02/2026 Distributor: Parchem

17/4/26